



**Transmittance Characteristics
of U.S. Army Rotary-Wing Aircraft Transparencies**

By

**Sean L. Wentworth
Everette McGowin III
Rebecca H. Ivey
Clarence E. Rash
William E. McLean**

Aircrew Health and Performance Division

March 1995

Approved for public release; distribution unlimited.

**United States Army Aeromedical Research Laboratory
Fort Rucker, Alabama 36362-0577**

Notice

Qualified requesters

Qualified requesters may obtain copies from the Defense Technical Information Center (DTIC), Cameron Station, Alexandria, Virginia 22314. Orders will be expedited if placed through the librarian or other person designated to request documents from DTIC.

Change of address

Organizations receiving reports from the U.S. Army Aeromedical Research Laboratory on automatic mailing lists should confirm correct address when corresponding about laboratory reports.

Disposition

Destroy this document when it is no longer needed. Do not return it to the originator.

Disclaimer

The views, opinions, and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy, or decision, unless so designated by other official documentation. Citation of trade names in this report does not constitute an official Department of the Army endorsement or approval of the use of such commercial items.

Human use


Human subjects participated in these studies after giving their free and informed voluntary consent. Investigators adhered to AR 70-25 and USAMRDC Reg 70-25 on Use of Volunteers in Research.

Reviewed:




RICHARD R. LEVINE
LTC, MS
Director, Aircrew Health and
Performance Division

Released for publication:

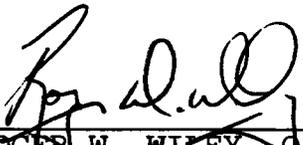

ROGER W. WILEY, O.D., Ph.D.
Chairman, Scientific
Review Committee



DENNIS F. SHANAHAN
Colonel, MC, MFS
Commanding

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS										
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION / AVAILABILITY OF REPORT Approved for public release, distribution unlimited										
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE												
4. PERFORMING ORGANIZATION REPORT NUMBER(S) USAARL Report No. 95-19		5. MONITORING ORGANIZATION REPORT NUMBER(S)										
6a. NAME OF PERFORMING ORGANIZATION U.S. Army Aeromedical Research Laboratory	6b. OFFICE SYMBOL (if applicable) MCMR-UAD	7a. NAME OF MONITORING ORGANIZATION U.S. Army Medical Research and Materiel Command										
6c. ADDRESS (City, State, and ZIP Code) P.O. Box 620577 Fort Rucker, AL 36362-0577		7b. ADDRESS (City, State, and ZIP Code) Fort Detrick Frederick, MD 21702-5012										
8a. NAME OF FUNDING / SPONSORING ORGANIZATION	8b. OFFICE SYMBOL (if applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER										
8c. ADDRESS (City, State, and ZIP Code)		10. SOURCE OF FUNDING NUMBERS <table border="1" style="width: 100%; border-collapse: collapse; margin-top: 5px;"> <tr> <th style="width: 25%;">PROGRAM ELEMENT NO.</th> <th style="width: 25%;">PROJECT NO.</th> <th style="width: 25%;">TASK NO.</th> <th style="width: 25%;">WORK UNIT ACCESSION NO.</th> </tr> <tr> <td style="text-align: center;">0602787A</td> <td style="text-align: center;">3M162787AA879</td> <td style="text-align: center;">PE</td> <td style="text-align: center;">164</td> </tr> </table>		PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT ACCESSION NO.	0602787A	3M162787AA879	PE	164	
PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT ACCESSION NO.									
0602787A	3M162787AA879	PE	164									
11. TITLE (Include Security Classification) (U) Transmittance Characteristics of U.S. Army Rotary-Wing Aircraft Transparencies												
12. PERSONAL AUTHOR(S) Sean Wentworth, Everette McGowin, III, Rebecca Ivey, Clarence Rash, William McLean												
13a. TYPE OF REPORT Final	13b. TIME COVERED FROM TO	14. DATE OF REPORT (Year, Month, Day) 1995 March	15. PAGE COUNT 29									
16. SUPPLEMENTAL NOTATION												
17. COSATI CODES <table border="1" style="width: 100%; border-collapse: collapse; margin-top: 5px;"> <thead> <tr> <th style="width: 33%;">FIELD</th> <th style="width: 33%;">GROUP</th> <th style="width: 33%;">SUB-GROUP</th> </tr> </thead> <tbody> <tr> <td style="text-align: center;">13</td> <td style="text-align: center;">06</td> <td></td> </tr> <tr> <td style="text-align: center;">14</td> <td style="text-align: center;">04</td> <td></td> </tr> </tbody> </table>		FIELD	GROUP	SUB-GROUP	13	06		14	04		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number) Windscreen, transparency, optical testing	
FIELD	GROUP	SUB-GROUP										
13	06											
14	04											
19. ABSTRACT (Continue on reverse if necessary and identify by block number) This report documents a survey of the spectral and luminous transmittance characteristics of transparencies (windscreens) used in currently fielded U.S. Army rotary-wing aircraft. The survey was conducted in two phases. In the first phase, samples of windscreens from each aircraft type were evaluated in the laboratory for photopic (day) and scotopic (night) luminous transmittance. The spectral transmittance of each sample also was measured. Based on laboratory measurements of unused samples, all windscreens met specifications. However, field measurements on windscreens showed consistent failure of luminous transmittance requirements. This loss of transmittance is attributed to haze resulting from exposure to environmental factors.												
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified										
22a. NAME OF RESPONSIBLE INDIVIDUAL Chief, Science Support Center		22b. TELEPHONE (Include Area Code) (334) 255-6907	22c. OFFICE SYMBOL MCMR-UAX-SS									

Table of contents

	Page no.
List of tables	2
Introduction	3
Specifications and requirements	3
Methodology	9
Spectral transmittance	9
Luminance transmittance	10
Field measurements	10
Data	10
Spectral transmittance	10
Luminous transmittance	19
Summary	23
References	24
Appendix A - List of transparency manufacturers	26
Appendix B - List of equipment manufacturers	29

List of figures

Figure no.	Page no.
1. The AH-1 Cobra	4
2. The AH-64 Apache	4
3. The CH-47D Chinook	5
4. The OH-6 Cayuse	5
5. The OH-58A Kiowa	6
6. The OH-58C Kiowa	6
7. The OH-58D Kiowa	7

List of figures (Continued).

Figure no.	Page no.
8. The TH-67 Creek	7
9. The UH-1 Iroquois	8
10. The UH-60 Black Hawk	8
11. Spectral transmittance curve for AH-1 Cobra	11
12. Spectral transmittance curve for AH-64 Apache	12
13. Spectral transmittance curve for CH-47D Chinook	13
14. Spectral transmittance curve for OH-58A/D Kiowa	14
15. Spectral transmittance curve for OH-58C Kiowa	15
16. Spectral transmittance curve for TH-67 Creek	16
17. Spectral transmittance curve for UH-1 Iroquois	17
18. Spectral transmittance curve for UH-60 Black Hawk	18
19. Example of surface abrasion present in an AH-64 windscreen	23

List of tables

Table no.	Page no.
1. Luminous transmittance (in percent)	20
2. Field measurements of photopic luminous transmittance (in percent)	21
3. Comparison of laboratory and field photopic luminous transmittance measurements	22

Introduction

This report documents a survey of the spectral and luminous transmittance characteristics of transparencies (windscreens) used in currently fielded U.S. Army rotary-wing aircraft (AH-1 Cobra, AH-64 Apache, CH-47 Chinook, OH-6 Cayuse, OH-58A/C/D Kiowa, TH-67 Creek, UH-1 Iroquois, and UH-60 Black Hawk [Figures 1-10]). These characteristics are essential to addressing issues related to aviator and crewman visual performance. In addition, spectral transmittance characteristics impact the performance of helmet-mounted imaging systems, such as the AN/AVS-6 Aviator's Night Vision Imaging System (ANVIS).

Previous investigations of the optical characteristics of U.S. Army rotary-wing aircraft transparencies (Chiou, 1975, 1976; Chiou, Park, and Moser, 1976; Crosley, 1968) may no longer be representative of currently fielded transparencies. Manufacturers of U.S. Army aircraft transparencies often change with each procurement contract. Appendix A provides a list of current manufacturers.

The survey was conducted in two phases. In the first phase, samples of windscreens from each aircraft type were evaluated in the laboratory for photopic (day) and scotopic (night) luminous transmittance. The spectral transmittance of each sample also was measured.

Installed transparencies are exposed continuously to the environment, collision with airborne particulate matter, and the abuses which often accompany aircraft maintenance. Therefore, to provide a more realistic assessment of transmittance values as experienced in the field, a second phase consisting of field measurements of photopic luminous transmittance for windscreens installed on aircraft on the flight line was conducted.

The laboratory measurements were taken on new (or not previously used) transparency samples. Due to limited availability of such transparencies, only a single sample of each forward windscreen could be obtained for each aircraft type. [An exception to this was the inability to obtain any front windscreens of the OH-6 or the right front windscreen for the UH-60.] Therefore, the data reported herein should be considered only representative of transparency performance. Field measurements (photopic transmittance only) were made on six aircraft per type.

Specifications and requirements

MIL-W-81752A(AS), "Military specification: Windshield systems, fixed wing aircraft, general specification for,"



Figure 1. The AH-1 Cobra.



Figure 2. The AH-64 Apache.



Figure 3. The CH-47D Chinook.



Figure 4. The OH-6 Cayuse.



Figure 5. The OH-58A Kiowa.



Figure 6. The OH-58C Kiowa.



Figure 7. The OH-58D Kiowa.



Figure 8. The TH-67 Creek.



Figure 9. The UH-1 Iroquois.



Figure 10. The UH-60 Black Hawk.

requires attack type aircraft to have an average luminous transmittance of not less than 80 percent when measured at normal angles of incidence to the surface. Other aircraft are required to have an average luminous transmittance of not less than 60 percent when measured at normal angles of incidence to the surface.

During day flights, pilotage and other external tasks are primarily accomplished by naked eye viewing through the windscreens and windows. However, current U.S. Army doctrine requires pilots and crewmen to perform missions successfully during periods of low illuminance, e.g., at night and in foul weather. To achieve acceptable performance under these conditions, devices based on the principle of image intensification are used in the cockpit and crew areas. The most prominent of these devices is the ANVIS. This night vision system has a spectral response of 450-950 nanometers (nm) with an enhanced sensitivity from 625-900 nm (MIL-L-85762A). Windscreens and windows must provide adequate spectral transmittance over this latter spectral range to optimize ANVIS performance.

MIL-W-81752A(AS) states the windshield shall be (ANVIS) compatible over the wavelength range of 600-900 nanometers.

Methodology

Spectral transmittance

Spectral transmittance data were obtained in a darkened laboratory using an EG&G Gamma Scientific* model C-9 spectral scanning system and a model RS-1 tungsten source. Spectroradiometric data were measured over the wavelength range of 350-950 nanometers in 5-nm steps for the reference tungsten source alone and for each transparency sample/source combination. The transmittance curves were obtained by performing a division, by wavelength, of the transparency/source combination data by the source data.

A sample of the left front windscreen was measured in each aircraft with side-by-side seating. A lower front windscreen sample was measured for the attack aircraft, which have tandem seating. In order to minimize scratching of the unused transparencies during measurement, the protective sheeting was removed from as small an area as possible. Therefore, measurements were taken at arbitrary and different points on each samples. [Note: This was not considered to be a relevant factor since an investigation of several samples showed a variation of less than 5 percent across the sample. A similar investigation

*See Appendix B.

of the effect of slant (deviation from normal) also showed a variation of less than 5 percent.] Settings of 900 volts photomultiplier tube anode voltage and 1-degree aperture size on the collection optics were used.

Luminous transmittance

Photopic and scotopic luminous transmittance values were measured in a darkened laboratory using a Photo Research* model 1980A photometer and EG&G Gamma Scientific model RS-1 tungsten source. Following a prescribed warm-up period for the photometer and the reference lamp, luminous transmittance measurements were taken for each sample using the photopic and scotopic filters integral to the photometer. Each measurement consisted of reading the luminance of the reference lamp, placing the respective transparency sample normal to the optical path, and taking a second luminance reading. The transmittance was calculated by dividing the luminance value obtained of the sample/source combination by the value obtained of the source alone. Three readings were obtained for each sample. The mean of these three values was calculated and reported.

Field measurements

Field measurements of photopic transmittance values were acquired for six of each aircraft type on flight lines at U.S. Army airfields at Fort Rucker, Alabama. [Note: An exception was the OH-58C aircraft, where only four aircraft were measured.] Measurements were made using an EG&G Gamma RS-1 tungsten source powered by a field generator and a Minolta* 1-degree aperture luminance meter. Each measurement consisted of reading the luminance of the reference source alone and reading the reference source luminance from a position of the left seat for aircraft with side-by-side seating and from the front seat of aircraft with tandem seating. The transmittance was calculated by dividing the value obtained from the cockpit by the value of the source alone.


Data

Spectral transmittance

The transmittance curves for the windscreen sample are provided in Figures 11-18. The samples from AH-64 (except aft windscreen), CH-47, UH-1, and UH-60 aircraft were of glass composition. The AH-1, OH-58A/C/D, and TH-67 samples were of acrylic composition. All samples were of "clear" material except for the TH-67, which had a bluish tint.

TITLE: AH-1 Cobra
DEVICE: Cobra #0476/

DATE: 07-11-1994
MAX: .93869
MIN: .28553

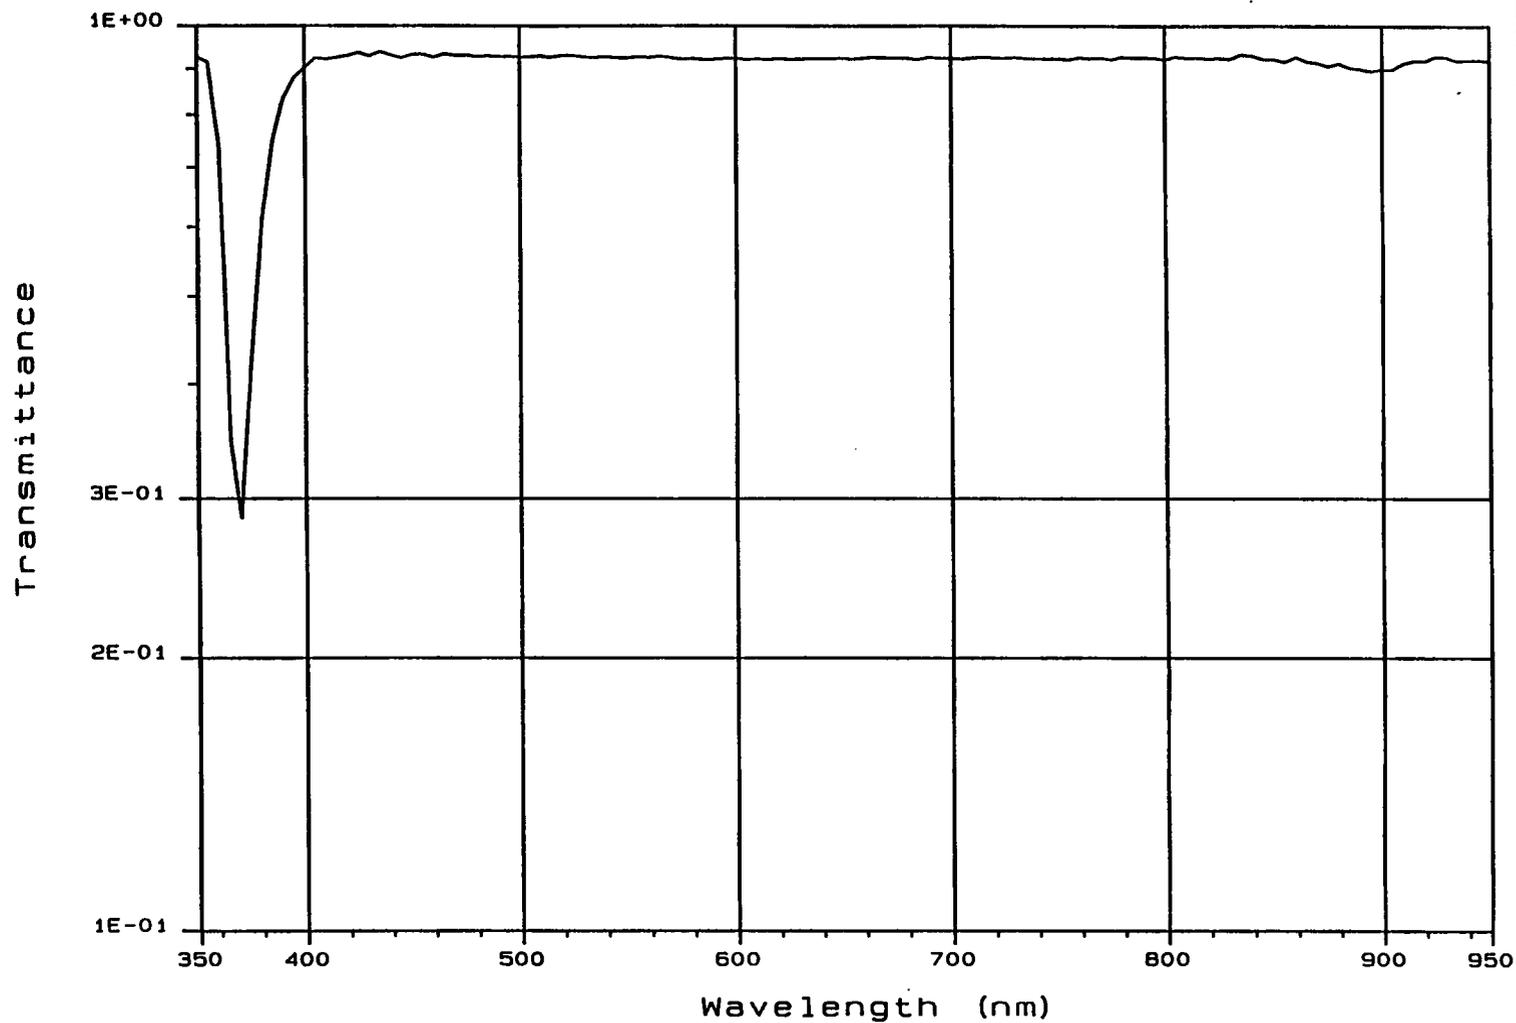


11

Figure 11. Spectral transmittance curve for AH-1 Cobra.

TITLE: AH-64 Apache
DEVICE: AH-64 (frwd) #7475/

DATE: 07-14-1994
MAX: .84769
MIN: .62242

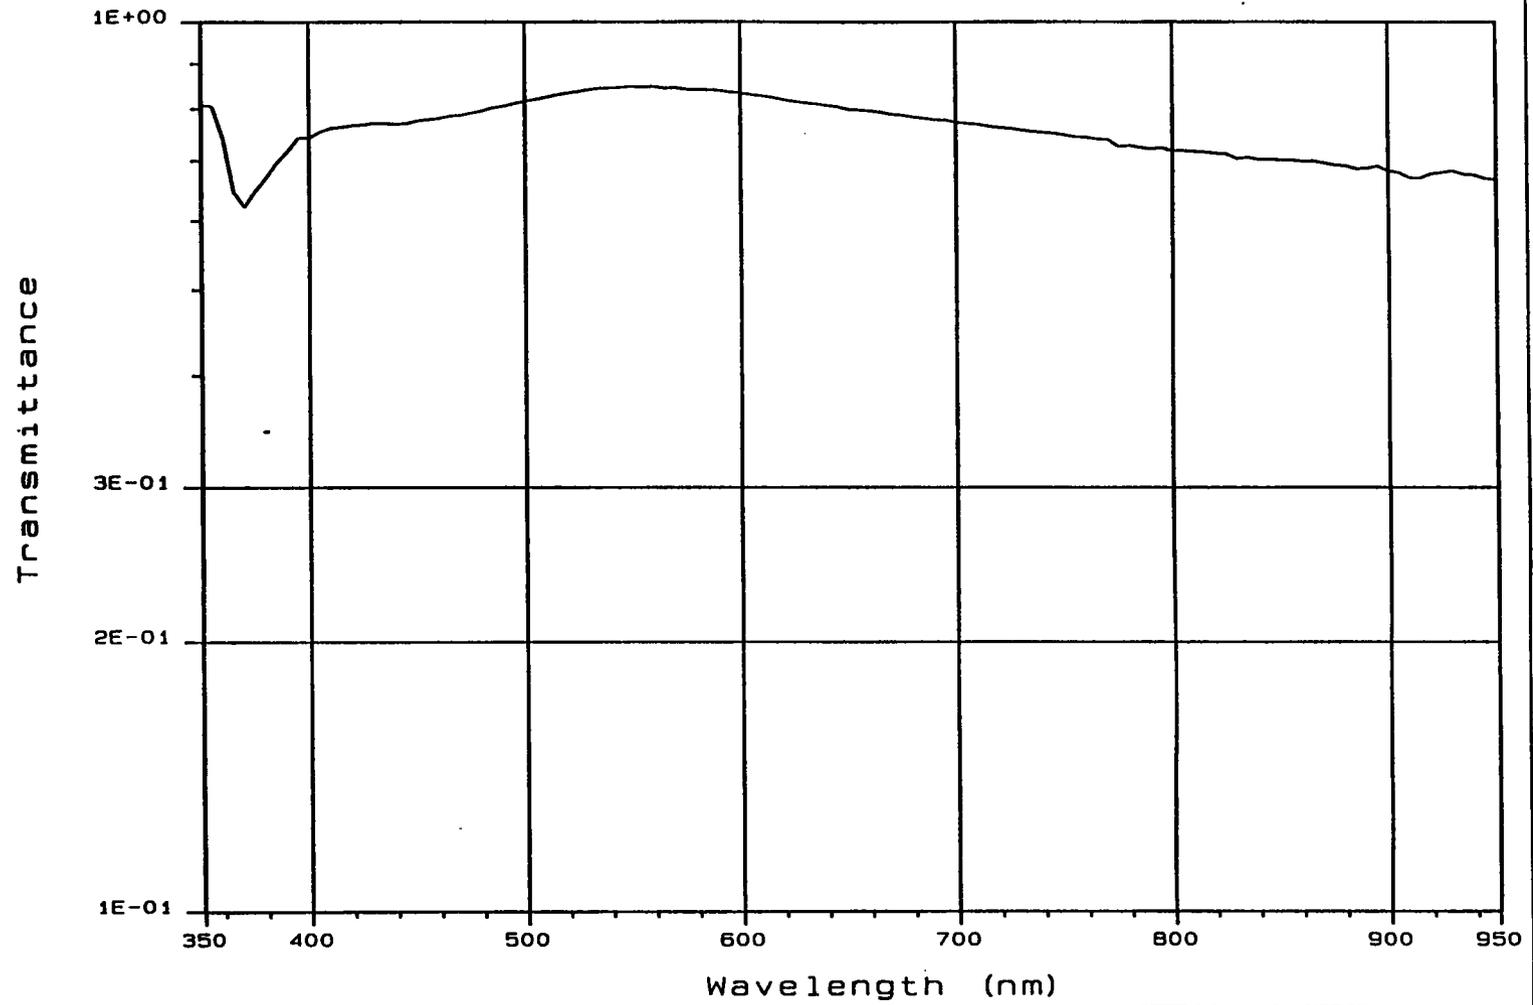


12

Figure 12. Spectral transmittance curve for AH-64 Apache.

TITLE: CH-47 Chinook
DEVICE: CH-47 #7857/

DATE: 07-11-1994
MAX: .86792
MIN: .66991

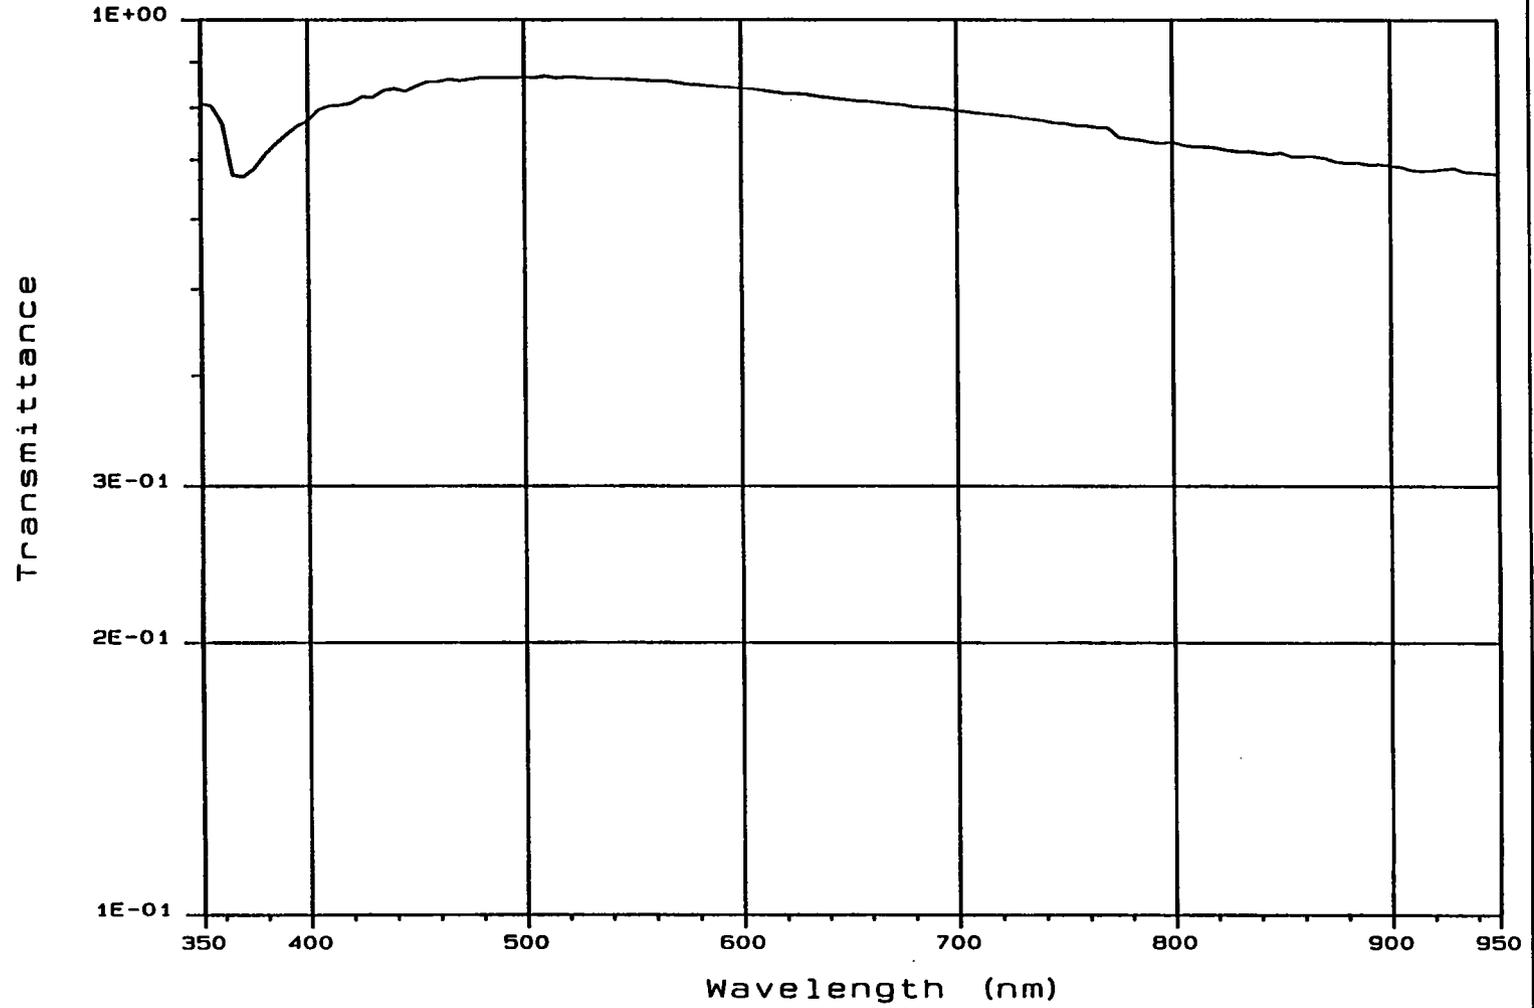


13

Figure 13. Spectral transmittance curve for CH-47D Chinook.

TITLE: OH-58 A&D Kiowa
DEVICE: OH-58 A&D (1&r) #3181/

DATE: 07-15-1994
MAX: .9059
MIN: .4368

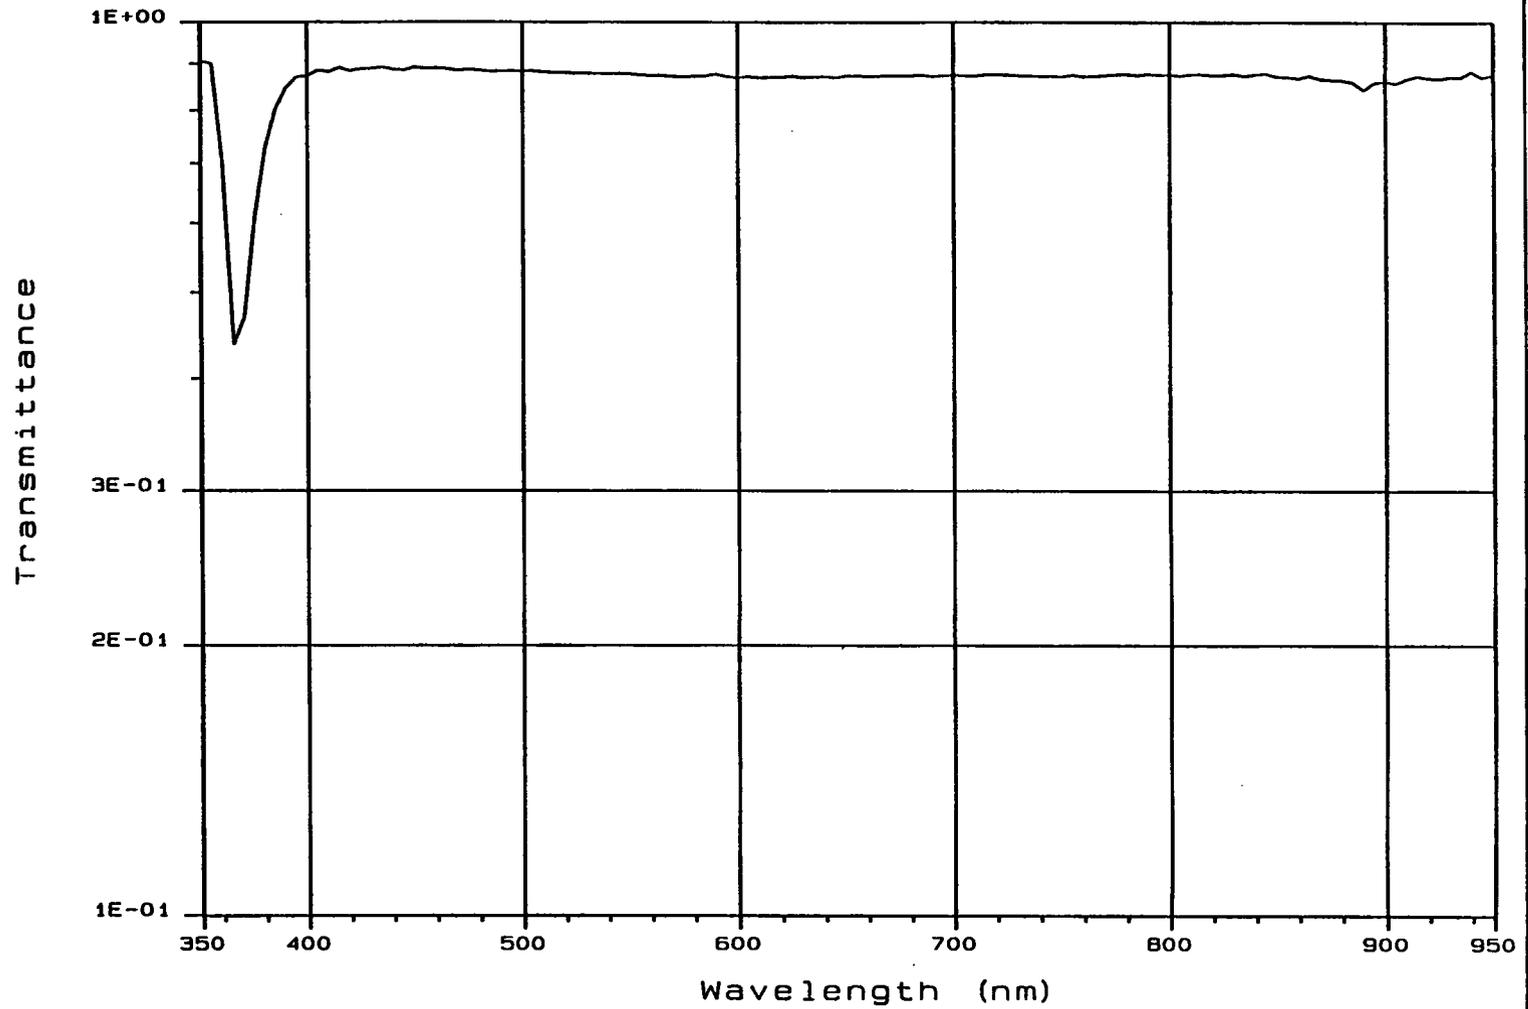


14

Figure 14. Spectral transmittance curve for OH-58A/D Kiowa.

TITLE: OH-58 C Kiowa
DEVICE: OH-58C (left) #5359/

DATE: 07-14-1994
MAX: .94996
MIN: .43017

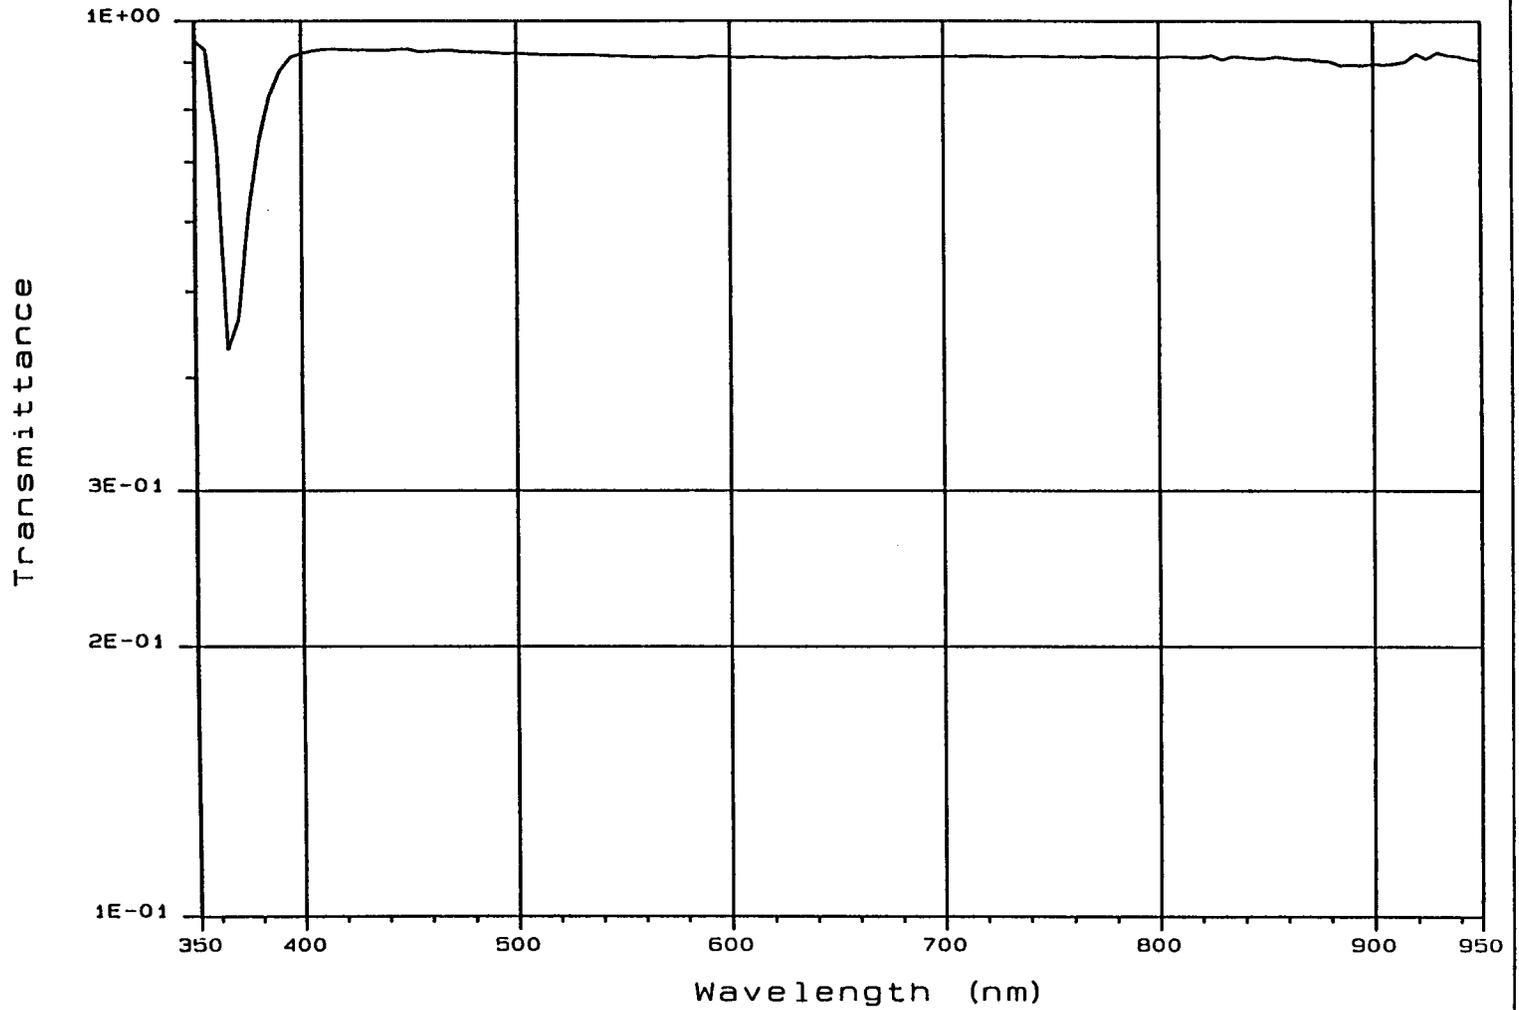


15

Figure 15. Spectral transmittance curve for OH-58C Kiowa.

TITLE: TH-67 Creek
DEVICE: TH-67 Front Left/

DATE: 08-04-1994
MAX: .92585
MIN: .202

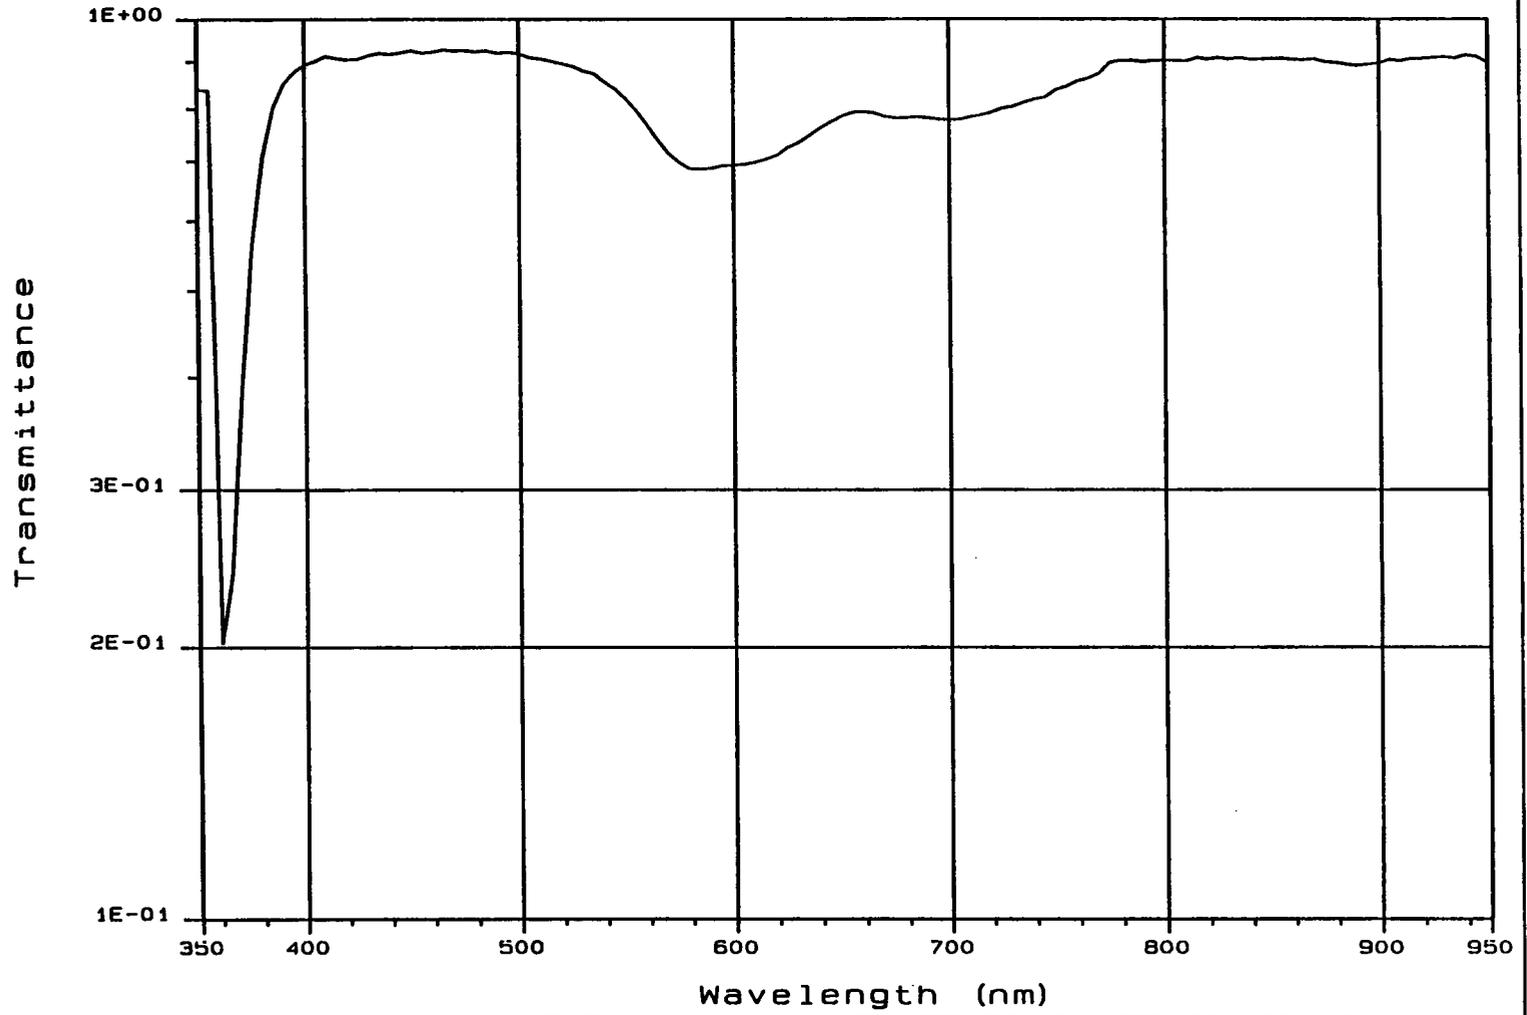


16

Figure 16. Spectral transmittance curve for TH-67 Creek.

TITLE: UH-1 Iroquois
DEVICE: UH-1 Front Left/

DATE: 08-04-1994
MAX: .88593
MIN: .68467

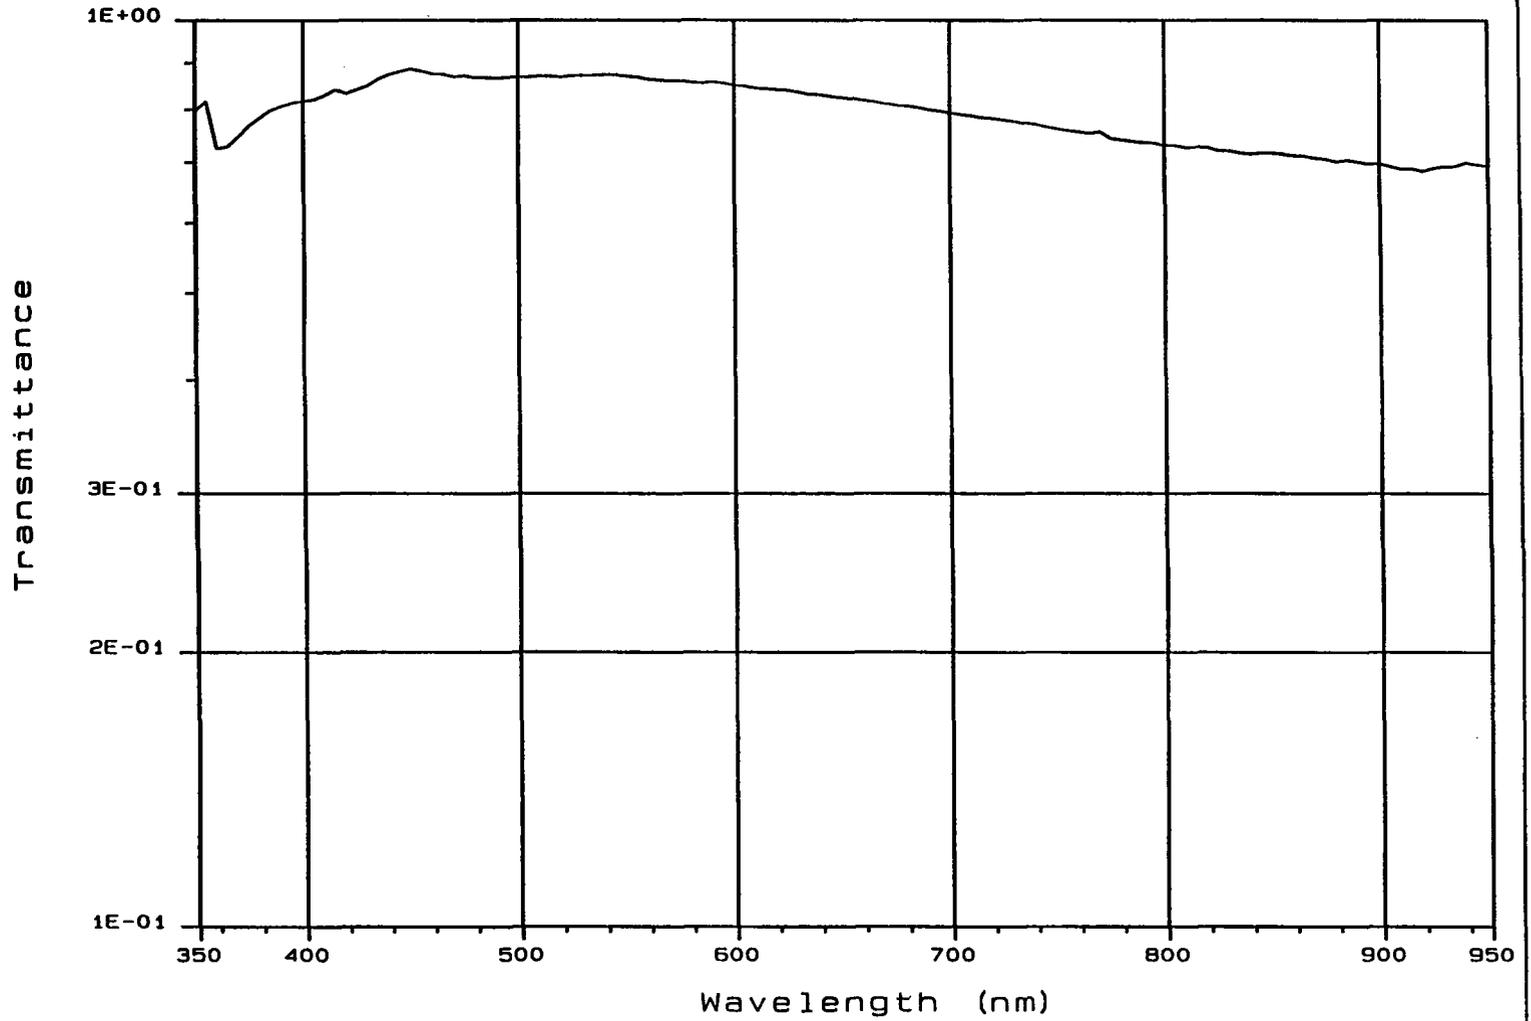

17

Figure 17. Spectral transmittance curve for UH-1 Iroquois.

TITLE: UH-60 Black Hawk
DEVICE: UH-60 (left) #2249/

DATE: 07-13-1994
MAX: .7692
MIN: .50154

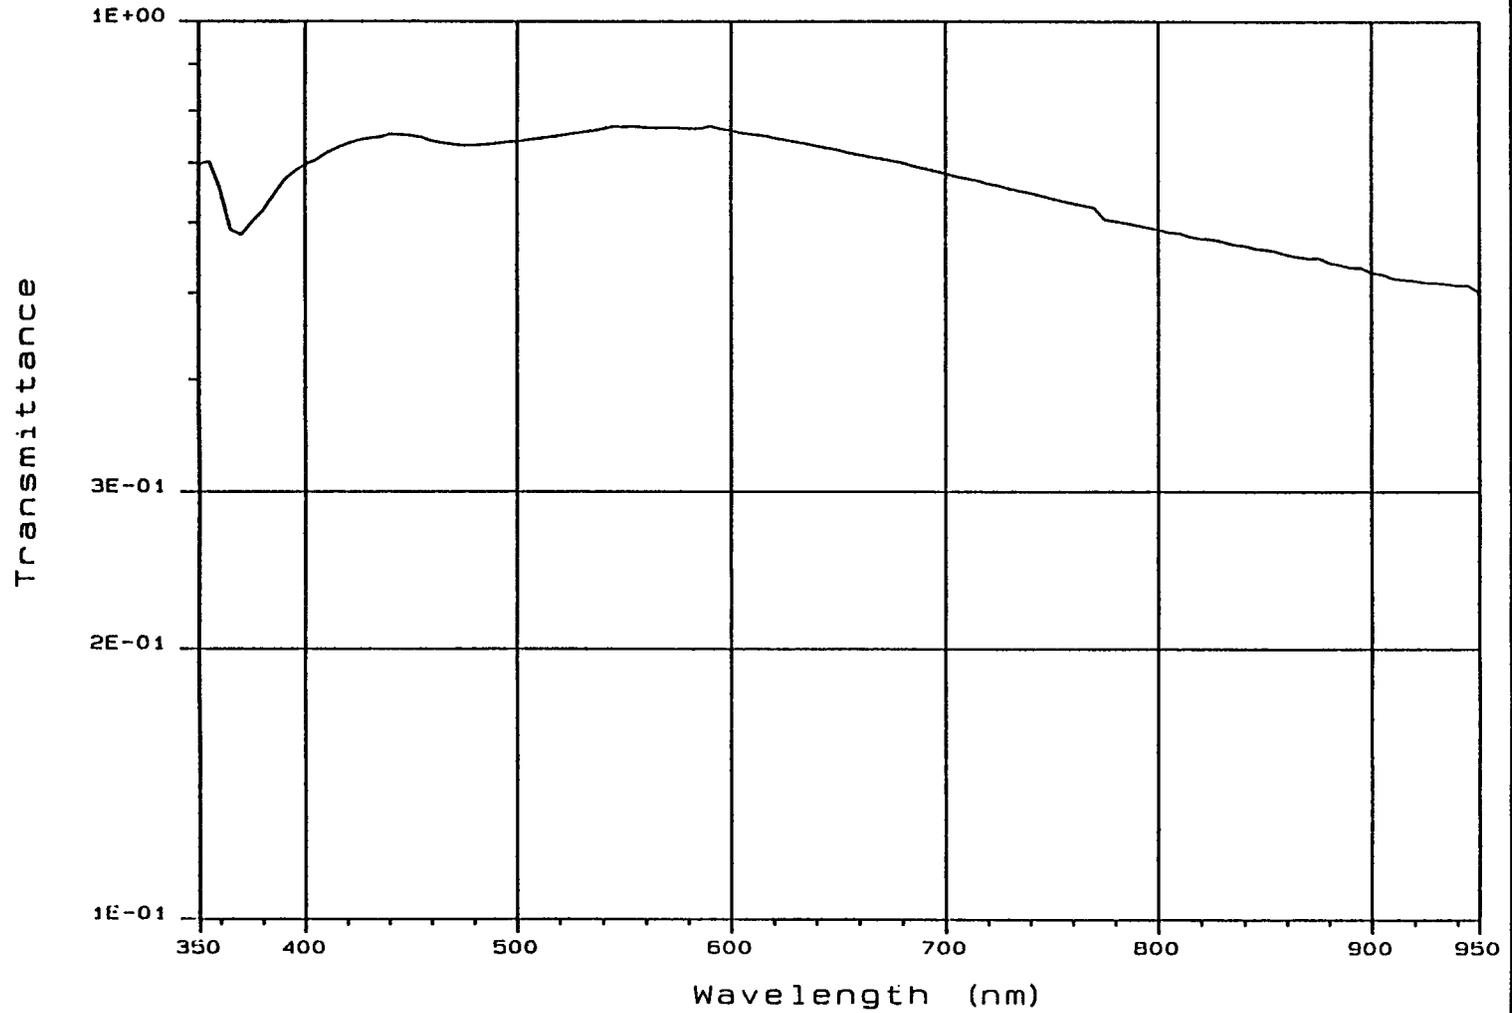


Figure 18. Spectral transmittance curve for UH-60 Black Hawk.

The spectral curves in Figures 11-18 correspond to the descriptions above. The curves for the AH-1, OH-58, and TH-67 samples demonstrate the spectral transmittance characteristics of acrylic materials. These include an ultraviolet cut-off between 350-380 nm and excellent spectral neutrality (flatness of transmittance) over the visible spectral range 400-780 nm. These acrylic windscreens also provide high, relatively flat, transmittance over the spectral response range of the ANVIS, 450-930 nm. The TH-67 sample has a deviation from neutrality over the range 560-780 nm (Figure 16). This decrease in transmittance of the red wavelengths produces the bluish color of the tint.

The glass samples of the AH-64, CH-47, UH-1, and UH-60 also provide a relatively neutral transmittance over the measured spectral range with a similar UV cutoff around 360 nm, but present some relative falloff in transmittance beyond 600 nm. This is of little significance to naked eye vision, which peaks at 550 nm. It also has little effect on ANVIS performance, which has enhanced sensitivity over the spectral range of 625-900 nm.

Note 1: The OH-6, while not available for laboratory measurement of spectral transmittance, is manufactured from acrylic material and should have optical characteristics similar to the AH-1, OH-58A, and TH-67 samples.

Note 2: The apparent increase of transmittance below 360 nm present in the curves is an artifact of the collection optics and spectral sensitivity of the spectroradiometer.

Luminous transmittance

Clear glass materials typically provide 80 to 92 percent photopic luminous transmittance; acrylic typically provides 85 to 92 percent (IES, 1984). The photopic and scotopic luminous values obtained in the laboratory measurements are presented in Table 1. The photopic values ranged from 73 to 93 percent; scotopic values ranged from 81 to 91 percent. When the TH-67 tinted samples are excluded, the photopic values for the glass samples ranged from 82 to 88 percent and the values for the acrylic samples ranged from 90 to 93 percent. The lowest photopic values, 73 and 77 percent, were for the tinted TH-67 samples.

The scotopic values generally tracked within a few percentage points of their corresponding photopic values. This was due to the flatness of the transmittance properties of glass and acrylic. The exception, as noted, of the TH-67 samples and their attenuation of red light produced higher scotopic values.

Based on the laboratory measurements, all of the tested windscreen samples met the requirements of MIL-W-81752A(AS).

The photopic luminous transmittance values obtained for flight line aircraft are presented in Table 2. These values ranged from 58 to 84 percent.

Table 1.

Luminous transmittance (in percent).

Aircraft	Panel position and FSN*	Photopic	Scotopic
AH-1	front 1560-01-028-0476	92	91
AH-64	forward 1560-01-170-7475	82	81
AH-64	center 1560-01-170-7474	82	81
AH-64	aft 1560-01-165-9621	88	89
CH-47	right 1560-00-133-7158	83	82
CH-47	center 1560-00-113-7857	85	87
CH-47	left 1560-00-133-7157	82	82
OH-6	left 1560-00-133-6186	**	**
	right 1560-00-133-6229		
OH-58A	right 1560-00-127-3179	90	91
OH-58A	left 1560-00-127-3181	92	91
OH-58C	right 1560-01-070-5360	92	91
OH-58C (curved)	left 1560-01-070-5359	92	91
OH-58D	right 1560-00-127-3179	90	91
OH-58D	left 1560-00-127-3181	92	91
TH-67	right 206-031-115-105	73	82
TH-67	left 206-031-115-0335	77	85
UH-1	right 1560-00-433-7271	89	89
UH-1	left 1560-00-433-7321	93	89
UH-60	right 1560-01-084-2250	**	**
UH-60	center 1560-01-207-7485	82	82
UH-60	left 1560-01-084-2249	84	81

* Federal stock number; for TH-67, manufacturer part number is given.

** Samples of OH-6 and OH-58 flat windscreens and the right front UH-60 windscreen were not available.

Table 2.

Field measurements of photopic luminous transmittance
(in percent).

Aircraft windscreen	Photopic transmittances (in percent)	Mean	Standard deviation
AH-1 front bottom	83, 75, 76, 81, 77, 82	79	3.4
AH-64 front bottom	71, 67, 76, 72, 73, 70	72	3.0
CH-47 front left	--, 62, 68, 70, 63, 48*	66	3.9
OH-6 front left	80, 70, 67, 70, 71, 75	72	4.6
OH-58A front left	77, 77, 75, 78, 76, 75	76	1.2
OH-58C curved front left	53, 62, 59, 58*	58	3.7
OH-58C flat front left	70, 60, 58, 63, 58, 66	63	4.8
OH-58D front left	71, 72, 73, 74, 70, 76	73	2.2
TH-67 front left	65, 64, 62, 64, 63, 67	64	1.7
UH-1 front left	83, 86, 84, 82, 84, 84	84	1.3
UH-60 front left	5, 75, 75, 71, 74, 75	74	1.6

* Note: For the CH-47, the first reading was invalid due to a recording error and for the last reading, condensation on the interior of windscreen produced an erroneous value; neither value is shown in the table. For the OH-58C with curved windscreen, only four aircraft were available for measurement. These windscreens exhibited significant levels of abrasion and the obtained values were further affected by condensation and fogging.

In Table 3, a comparison between the laboratory and field photopic luminous transmittance values (for front left windscreens) is presented. The percent decrease in photopic transmittance between the unused and fielded windscreens are presented in the last column. In each case, the field value decreased from the laboratory value. Percent decrease

Table 3.

Comparison of laboratory and field photopic luminous transmittance measurements.

Aircraft	Laboratory value	Field value	Percent decrease
AH-1	92	79	14
AH-64	82	72	12
CH-47	83	66	20
OH-6	--	72	--
OH-58A	92	76	17
OH-58C curved	92	58	37
OH-58C flat	--	63	--
OH-58D	92	73	21
TH-67	77	64	17
UH-1	93	84	10
UH-60	84	74	12

Note: Unused samples of OH-6 and OH-58C flat windscreens were not available.

ranged from 10 percent for the UH-1 to 37 percent for the OH-58C (curved). The mean percent decrease was 18 percent. (If the relatively large percent decrease value of 37 for the OH-58C is excluded, the mean percent decrease was 15 percent.) Several factors attributed to this decrease. As would be expected under field conditions, the windscreens were dirty both inside and outside. In addition, because the field measurements were

taken at night, condensation and fogging also were present in varying degrees. These factors, while contributing, are considered secondary to the effects of haze resulting from the highly abraded external surfaces of the windscreens. Figure 19 shows an example of an AH-64 windscreen having a significant level of abrasion.

Summary

All of the windscreen samples (except for the tinted TH-67) were found to be spectrally neutral over the visible spectrum. Likewise, all samples indicated sufficient spectral transmittance over the spectral range required for optimal performance of ANVIS.

For luminous transmittance, all of the unused samples measured in the laboratory met the requirements of MIL-W-81752A(AS). However, an analysis of the field measurements of



Figure 19. Example of surface abrasion present in an AH-64 windscreen.

luminous transmittance, while qualified by the small sample size, shows significant decreases in transmittance for all windscreen types. These decreases are considered to be caused by haze resulting from the physical abuse to which the windscreens are subjected.

The governing specifications require attack aircraft to have an average luminous transmittance of not less than 80 percent and nonattack aircraft to have not less than 60 percent. All windscreen samples met this requirement in the laboratory measurements. However, based on field measurements, neither attack aircraft, the AH-1 or AH-64, met the 80 percent requirement. The OH-58C curved windscreens, with a mean value of 58 percent, failed to meet the 60 percent requirement for nonattack aircraft. The conclusion which can be drawn from this study seems to be that all windscreen samples meet the specification for luminous transmittance upon delivery, but during usage degrade in performance. Since data were not available to correlate performance degradation with length of service, it is not possible to formulate a recommendation on how often to replace the windscreens. However, it is obvious from the data that in the harsh environments of military flight, the optical performance of the windscreens does degrade below that required by the specification and this situation warrants a policy of closer inspection at the unit level.

References

- Chiou, W. C. 1975. Visible spectral transmission characteristics of windscreens in Army aircraft. Fort Rucker, AL: U.S. Army Aeromedical Research Laboratory. USAARL LR-75-29-7-8
- Chiou, W. C. 1976. Visible and near infrared spectral transmission characteristics of windscreens in Army aircraft. Fort Rucker, AL: U.S. Army Aeromedical Research Laboratory. USAARL Report 76-14.
- Chiou, W. C., Park, C. K., and Moser, C. E. 1976. Attenuation of light transmission in Army aircraft transparencies due to slating. Fort Rucker, AL: U.S. Army Aeromedical Research Laboratory. USAARL Report 76-23
- Crosley, J. K. 1968. Tinted windscreens in U.S. Army aircraft. Fort Rucker, AL: U.S. Army Aeromedical Research Laboratory. USAARU Report No. 68-7
- Department of Defense. 1988. Military specification: Lighting, aircraft, interior, night vision imaging system compatible. Washington, DC: Department of Defense. MIL-L-85762A.

Department of Defense. 1988. Military specification: Windshield systems, fixed wing aircraft, general specification for. Washington, DC: Department of Defense. MIL-W-81752A(AS), Amendment 1.

Illuminating Engineering Society (IES) of North America. 1984. IES lighting handbook. J. E. Kaufman, editor. New York, NY: IES of North America.

Appendix A

List of transparency manufacturers.

AH-1

Bell Helicopter Textron, Inc.
600 E Hurst Blvd.
P.O. Box 482
Fort Worth, TX 76101-8020
(817)280-2011

LP Aero Plastics Inc.
Road 1
P.O. Box B
Jeannette, PA 15644-9730
(412)744-4448

AH-64

McDonald Douglas Helicopter Co.
Sub of McDonald Douglas Corp.
6775 Centinela Ave.
Culver City, CA 90230-6370
(310)305-6562

PPG
Aircraft Product Sales
1719 Highway 72E
P.O. Box 040004
Huntsville, AL 35804
(205)851-7001

CH-47

PPG
Aircraft Product Sales
1719 Highway 72E
P.O. Box 2200
Huntsville, AL 35804
(205)859-2500

Boeing Helicopter
Division of the Boeing Co.
Boeing Center
Industrial Hwy Bldg 3-25
Ridley Park, PA 19078
(215)591-3010

Appendix A (Continued)

List of transparency manufacturers

OH-6

McDonnell Douglas Helicopter Co.
6775 Centinela Ave.
Culver City, CA 90230-6370
(310)305-6562

Ten Cate Aerospace Inc.
5101 Blue Mound Rd.
Fort Worth, TX 76106

Texstar
802 Ave. J East
Grand Prairie, TX 75050-2552
(214)647-1366

OH-58

Bell Helicopter Textron Inc.
600 E Hurst Blvd.
P.O. Box 482
Fort Worth, TX 76101-8020
(817)280-2011

Texstar, Inc.
802 Ave. J East
Grand Prairie, TX 75050-2552
(214)647-1366

TH-67

Bell Helicopter Textron Inc.
600 E Hurst Blvd.
P.O. Box 482
Fort Worth, TX 76101-8020
(817)280-2011

UH-1

PPG Industries, Inc.
Aircraft Product Sales
1719 Highway 72 E
P.O. Box 040004
Huntsville, AL 35804
(205)851-7001

Appendix A (Continued)

List of transparency manufacturers

UH-60

PPG Industries, Inc.
1 PPG PL
Pittsburgh, PA 15272-0001
(412)434-3131

PPG
1719 Highway 72E
P.O. Box 2200
Huntsville, AL 35804
(205)859-8500

Davis Aircraft Product Co. Inc.
1150 Walnut Avenue
P.O. Box 525
Bohemia, NY 11716-2105
(516)563-1500

Appendix B

List of equipment manufacturers

EG&G Gamma Scientific Inc.
3777 Ruffin Rd.
San Diego, CA 92123

Minolta Corporation
101 Williams Drive
Ramsey, NJ 07446

Photo Research
Division of Kollmorgen
9330 DeSoto Ave.
P.O. Box 2192
Chatsworth, CA 91313-2192